

REPORT DOCUMENTATION PAGE

DTIC FILE COPY

AD-A224 927

AD-A224 927			1b. RESTRICTIVE MARKINGS			
			3. DISTRIBUTION / AVAILABILITY OF REPORT Approved for release: Distribution unlimited			
			5. MONITORING ORGANIZATION REPORT NUMBER(S) 3			
4. PERFORMING ORGANIZATION REPORT NUMBER(S) 3			6a. NAME OF PERFORMING ORGANIZATION Department of Chemistry Rice University, Houston			
6b. OFFICE SYMBOL (If applicable)			7a. NAME OF MONITORING ORGANIZATION Office of Sponsored Research Rice University P.O. Box 2692			
6c. ADDRESS (City, State, and ZIP Code) Houston, Texas 77251			7b. ADDRESS (City, State, and ZIP Code) Houston, Texas 77252			
8a. NAME OF FUNDING / SPONSORING ORGANIZATION Office of Naval Research			8b. OFFICE SYMBOL (If applicable)			9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N00014-88-K-0553
8c. ADDRESS (City, State, and ZIP Code) Chemistry Division 800 N. Quincy Street Arlington, VA 22217-5000			10. SOURCE OF FUNDING NUMBERS			
			PROGRAM ELEMENT NO 412m007	PROJECT NO	TASK NO	WORK UNIT ACCESSION NO
11. TITLE (Include Security Classification) Ultraviolet Photoelectron Spectra of Gallium Arsenide Clusters						
12. PERSONAL AUTHOR(S) C. Jin, K. J. Taylor, J. Conceicao and R. E. Smalley						
13a. TYPE OF REPORT Interim/Technical		13b. TIME COVERED FROM TO		14. DATE OF REPORT (Year, Month, Day) July 23, 1990		15. PAGE COUNT 15
16. SUPPLEMENTARY NOTATION Chem. Phys. Letters (1990)						
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)			
FIELD	GROUP	SUB-GROUP	Surface chemistry; ultraviolet photoelectron spectra UPS; Gallium arsenide clusters			
19. ABSTRACT (Continue on reverse if necessary and identify by block number) The ultraviolet photoelectron spectra (UPS) of mass-selected negative gallium arsenide cluster ions in the 2-50 atom size range was measured with a photon energy of 7.9 eV. The measured photodetachment thresholds displayed a strong even/odd oscillation through the largest clusters in this range, suggesting the presence of a substantial HOMO-LUMO gap in the corresponding neutral clusters which evolves to the band gap of bulk GaAs crystals.						
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION Unclassified			
22a. NAME OF RESPONSIBLE INDIVIDUAL Richard E. Smalley			22b. TELEPHONE (Include Area Code) (713) 527-4845		22c. OFFICE SYMBOL	

DTIC
ELECTE
AUG 8 1990
S B D

OFFICE OF NAVAL RESEARCH

CONTRACT N00014-88-K-0553

R&T Code 412m007

Technical Report No. 3

Ultraviolet Photoelectron Spectra of Gallium Arsenide
Clusters

by

C. Jin, K. J. Taylor, J. Conceicao, and R. E. Smalley

Chem. Phys. Letters (1990)

Rice University
Department of Chemistry
Houston, Texas

July 23, 1990

Reproduction in whole or in part is permitted for
any purpose of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited

ABSTRACT

The ultraviolet photoelectron spectra (UPS) of mass-selected negative gallium arsenide cluster ions in the 2-50 atom size range was measured with a photon energy of 7.9 eV. The measured photodetachment thresholds displayed a strong even/odd oscillation through the largest clusters in this range, suggesting the presence of a substantial HOMO-LUMO gap in the corresponding neutral clusters which evolves to the band gap of bulk GaAs crystals.

Accession For	
NTIS GRA&I	<input checked="checked" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

Chem. Phys. Lett.

submitted July, 1990

ULTRAVIOLET PHOTOELECTRON SPECTRA OF GALLIUM ARSENIDE CLUSTERS

C. Jin, K. J. Taylor¹, J. Conceicao², and R. E. Smalley

Rice Quantum Institute

and

Departments of Chemistry and Physics

Rice University

Houston, Texas 77251

ABSTRACT

The ultraviolet photoelectron spectra (UPS) of mass-selected negative gallium arsenide cluster ions in the 2-50 atom size range was measured with a photon energy of 7.9 eV. The measured photodetachment thresholds displayed a strong even/odd oscillation through the largest clusters in this range, suggesting the presence of a substantial HOMO-LUMO gap in the corresponding neutral clusters which evolves to the band gap of bulk GaAs crystals.

¹ present address: Texas Instruments, Dallas, Texas;

² Robert A. Welch Predoctoral Fellow.

INTRODUCTION

Nearly five years ago in an initial supersonic cluster beam experiment with gallium arsenide clusters, O'Brien *et al.*¹ discovered a remarkable even/odd alternation in the ionization potentials (IP). Since the clusters were prepared by laser vaporization of a gallium arsenide disc in a high pressure pulsed supersonic nozzle, the clusters formed in a highly supersaturated vapor of gallium and arsenic atoms, and a wide range of Ga_xAs_y compositions were generated for every cluster size, $n = x+y$. Even so the remarkable observation was made that all even numbered clusters in the size range from 4 to 22 atoms had IPs higher than 6.4 eV, while the odd-numbered clusters with 5-21 atoms all had IPs less than 6.4 eV. Somewhat later Liu *et al.*² reported results from a crude bracketing of the thresholds for photodetachment of electrons from the negative cluster ions of Ga_xAs_y in the 2-30 atom size range, thereby providing rough estimates of the vertical electron affinity (EA). Again even/odd alternation appeared, with the odd-numbered clusters having the larger EA values.

Such even/odd alternation in IP and EA as a function of cluster size has been a common observation in single-valence- electron metal clusters such as Na,³ K,⁴ Cu,⁵ Ag, and Au.⁶ In these metal clusters the even/odd alternation arises because the atomic valence orbitals are strongly overlapping and for the small clusters a substantial gap exists between the highest occupied molecular orbital (HOMO) and the lowest unoccupied molecular orbital (LUMO). However, since these elements are all metallic in the bulk phase, it is perhaps not surprising that this HOMO-LUMO gap soon becomes small enough that even/odd alternation in the IP and EA is no longer observed. In the case of gold clusters the even/odd alternation in IP and EA is extremely pronounced for clusters in the 2-20 atom size range, but it is largely gone by the time the cluster size is greater than 40.

Gallium arsenide, on the other hand, is potentially a far more complex situation than these simple group IA and IB metals. In bulk form it is a direct band gap semiconductor with a band gap of roughly 1.5 eV.⁷ Cleavage of the surface along the (110) plane, for example, results in a surface with gallium or arsenic atoms each having a single sp^3 dangling bond. In the absence of relaxation this would leave a metallic surface density of states. However, relaxation does occur, leaving the surface gallium atoms with an unoccupied dangling bond, and the surface arsenic atoms with a dangling lone-pair. Such surface reorganizations effectively sweep the dangling bond states out of the gap in the surface density of states, producing a semiconducting surface.⁸⁻¹⁰ Similarly effective relaxations or reconstructions are thought to occur on the other low miller index surfaces of GaAs.

In the case of small gallium arsenide clusters it is important to establish how effectively surface reconstruction can heal the dangling bonds. Particularly in the case encountered with supersonic beam sources which produce clusters with a wide range of compositions, the question of surface reconstruction appears at first to be impossibly complex. Yet the strong even/odd alternation in IP and EA for these clusters suggests that this reconstruction may be highly efficient. If so, it is possible that the even/odd alternation in IP and EA will continue through very large clusters, extrapolating to the bulk band gap. The ultraviolet photoelectron spectra

(UPS) survey experiments presented below were designed to test this hypothesis.

EXPERIMENTAL

Gallium arsenide clusters were prepared in a supersonic beam by laser vaporization of an undoped GaAs wafer. The pulsed supersonic cluster nozzle used in this work has been described in detail elsewhere.⁶ Briefly, it involved the use of two fast pulsed valves of the magnetic "current loop" variety,^{11,12} bolted to opposite sides of a 1.5 cm wide Teflon nozzle block. The opposing gas flows from these two valves (pulse duration 125 microsecond, 0.12 cm³ atm flow per pulse) was synchronized to meet in a cylindrical "waiting room", 0.3 cm diameter, 1.0 cm long drilled into the center of the nozzle block. The rotating, translating GaAs target disc was mounted on the back of this block, and the Nd:YAG 2nd harmonic vaporization laser beam (10-15 mJ pulse⁻¹, 5 nsec duration) was directed down the axis of the supersonic beam apparatus through the cylindrical waiting room, and focussed to a 0.1 cm diameter spot on the GaAs target disc. Cluster ions formed from the vaporized GaAs plasma in the waiting room accelerated with the helium carrier gas through a 0.2 cm diameter orifice, and passed through a 6 cm long nozzle cone, 10° internal angle. The resulting supersonic jet was then skimmed by a conical skimmer 15 cm downstream from the exit of the nozzle cone. The negatively charged Ga_xAs_y⁻ clusters were then pulsed out of the beam with a tilted extraction stack¹³ operating at 1000 Volts, and directed the cluster ion beam into the magnetically-focussed time-of-flight UPS apparatus discussed in previous publications from this group.^{5,6,14} An F₂ excimer laser (photon energy 7.9 eV) was used for photodetachment of the mass-selected Ga_xAs_y⁻ clusters.

In earlier studies of Ga_xAs_y clusters in this group it was noted that the clusters tended to lose arsenic (probably in the form of As₂ and As₄) when heated.^{1,2,15} When the laser vaporization cluster nozzle is operated to yield a substantial number of cluster ions derived from the original laser-induced plasma ionization, much of the cluster growth occurs while the buffer gas temperature is rather high. In the case of GaAs this often produces Ga_xAs_y clusters for which the x:y composition distribution is peaked somewhat to the gallium rich side (x>y).¹⁵ For this reason we optimized the operation of the cluster nozzle to minimize this arsenic loss as much as possible. Nonetheless, it was clear from careful calibration of the mass spectra of the Ga_xAs_y⁻ cluster beams used in this study that the distributions were skewed to the gallium-rich side, the maximum occurring near the composition with y=x+2.

The UPS apparatus was calibrated by measurement of the spectrum of Au⁻ and using the published values for the EA,¹⁶ and the first few excited electronic states of the neutral atom.¹⁷ In this UPS apparatus the effective photoelectron resolution is dependent on the translational velocity of the cluster ions at the moment of photodetachment.⁵ For the clusters with less than 20 atoms we decelerated the negative cluster ion beam to the range of 100-200 eV. Above 20 atoms this velocity effect on the resolution was small enough that deceleration from the original 900 eV energy of the pulse extracted Ga_xAs_y⁻ beam was unnecessary. The effective resolution of the UPS apparatus for the data reported below was 0.05 to 0.1 eV. All the spectra reported below were recorded as the accumulation of data from 10⁴ pulses of the cluster beam apparatus with background photoelectrons subtracted on

alternate laser shots. The resultant photoelectron spectra were smoothed with a 0.05 eV square window function.

RESULTS AND DISCUSSION

Figures 1-3 present the recorded UPS spectra of mass-selected Ga_xAs_y^- clusters in the size range $x+y = 2$ through 50. With the exception of the UPS data for the two atom cluster (which refers to the GaAs^- diatomic), our mass resolution was insufficient to pick out a single x,y composition. For the larger clusters, even with orders of magnitude higher mass resolution it would have been impossible to select purely a single x,y composition from the Ga_xAs_y clusters due to the overlapping mass distributions caused by the ^{69}Ga and ^{71}Ga isotopes of gallium in natural abundance. Instead we timed the firing of the photodetachment laser to intersect the section of the cluster time-of-flight spectrum corresponding to the time calculated for the stoichiometric 1:1 composition. For the even numbered clusters we chose the photodetachment time appropriate to the $x=y$ composition of the mass-selected Ga_xAs_y^- clusters, for the odd numbered clusters we chose the time calculated for the $x=y+1$ cluster. It is therefore important in interpreting these spectra to realize that they pertain to a range of cluster compositions, and also most certainly to a range of isomeric structures for each of these compositions as well.

One of the virtues of photoelectron spectroscopy of the negative ions is that the photodetachment threshold provides a direct measure of the vertical electron affinity. In order to estimate the detachment thresholds on such a broad range of poorly resolved spectra we adopted the following simple approach. For each spectrum a straight line fit was made to the rising slope of the first significant spectral feature. The vertical electron affinity was then taken to be the baseline intercept of this straight line plus a constant offset of 0.35 eV as a crude correction for cluster temperature and instrument resolution effects. These EA estimates are tabulated in Table I, and plotted in Figure 4.

As expected from earlier work with GaAs negative clusters,² even/odd alternation is evident in the EA as a function of cluster size. Although there can certainly be some disagreement with our way of picking the thresholds, we believe any reasonable method will result in the same conclusion: the even/odd alternation in the vertical EA is strong, and this alternation persists without substantial narrowing at least through 50 atoms.

In the earlier photodetachment work of Liu et al.² some evidence was presented indicating that the EAs tended to decrease for a given cluster size as one examined Ga_xAs_y clusters with compositions of decreasing x/y ratio. With the current UPS work this effect was quite evident when spectra were taken from differing regions of the composition-broadened mass peaks for any particular cluster size. For example, Figure 5 shows the UPS patterns obtained for the 23 atom cluster at the masses approximately corresponding to (x,y) composition values of (18,5), (12,11), and (5,18), respectively. The variation in apparent vertical EA for these clusters is nearly 0.5 eV. As listed in Table I, similar results were obtained from spot checks of the composition variation of EA were made for a number of clusters. Although this variation in EA across compositions for a single cluster size is within a factor of two as large as the observed even/odd variation between different cluster sizes, it was always found to be monotonic, and the even/odd

alternation in EA was always evident as long as clusters of similar x/y composition ratios were compared.

For the small cluster in the 2-6 atom size range the mass resolution and isotopomer distributions are sufficiently narrow in the experiment to obtain highly structured UPS patterns for individual compositions. The spectrum shown in Fig. 1 for the diatomic is an example -- it is from the GaAs^- molecule. In accord with the assignment of the optical spectrum of the neutral molecule,¹⁸ and recent theoretical calculations,¹⁹⁻²⁰ this UPS pattern shows that GaAs has an open-shell triplet ground state with an EA which is actually higher than the next odd-numbered cluster. Of all the even-numbered Ga_xAs_y clusters we have studied, this diatomic is the sole exception to the rule of uniform even/odd alternation in the EA as a function of cluster size. Detailed analysis of these small Ga_xAs_y cluster UPS patterns will be reserved for a latter paper. High resolution study of such spectra should provide direct tests of theoretical calculations for these species.

SUMMARY

The UPS patterns of mass-selected Ga_xAs_y^- clusters near the x=y composition reveals an even/odd alternation in vertical electron affinity that persists without significant narrowing through clusters 50 atoms in size. Together with the corresponding odd/even alternation in ionization potentials discovered earlier,¹ these new EA data strongly support the notion that relaxation/reconstruction of the surface of these GaAs clusters is highly facile. With the sole exception of the GaAs dimer, all the even-numbered clusters appear to have closed-shell ground state singlet states (for the neutral clusters) with substantial HOMO-LUMO gaps. The odd-numbered clusters will of course be open shell species as neutrals simply by virtue of the fact that they have an odd number of electrons, but the observed alternation in the IP of the neutral clusters shows that the HOMO for the odd-numbered clusters is always less tightly bound than for the even-numbered clusters. Preliminary results from extended Huckel and local spin density calculations currently underway in this laboratory on gallium arsenide clusters in the 2-20 atom size range are in agreement with this interpretation.²¹ The unfilled HOMO of odd-numbered clusters tends to be a largely non-bonding molecular orbital with an energy slightly less than half the HOMO-LUMO gap of the adjacent even-numbered clusters of the same x/y composition. If this trend continues through large clusters, the EA of the even-numbered clusters should asymptotically approach the 4.07 eV electron affinity of the perfect bulk crystal, while the EA of the odd-numbered clusters should evolve to a value slightly below 4.8 eV (the bulk EA plus half the intrinsic band gap).

As was evident even in the rough EA bracketing results of Liu et al.² the electron affinity of gallium arsenide clusters plotted in Fig. 4 approaches the bulk value of 4.07 eV⁷ much more rapidly than is typical with simple metal clusters such as potassium⁴ or copper⁵. This is another indication that these small clusters are behaving as semiconductors. Since the screening length for semiconductors such as GaAs is much longer than the radius of clusters in the 2-100 atom size range, screening is far less important here than with metal clusters. Furthermore, any semiclassical model based on uniform charging of a sphere²² is unlikely to be effective for these semiconductor cluster ions since the extra charge is apt to be concentrated near a few surface corner atoms. For even the most perfect possible macroscopic GaAs crystal the corners between otherwise perfectly reconstructed

surface facets will act as shallow traps slightly below the bottom of the bulk conduction band. These corner traps are likely sites for localization of the excess charge of the negative ion. To the extent the charge is localized, it will not take a very large cluster to mimic this effect. For a variety of reasons, therefore, these small nanometer-scale clusters may be quite adequate models of much of the physics and chemistry that occurs on the surface of bulk gallium arsenide.

ACKNOWLEDGEMENT

We thank Ori Cheshnovsky and Tapani Laaksonen for valuable discussions on the evolution of EA with size in semiconductor clusters. This research was supported by the U. S. Army Research Office and the Robert A. Welch foundation, using a cluster UPS apparatus supported for the study of semiconductor clusters by the Office of Naval Research, and by the Department of Energy, Division of Chemical Sciences for the study of bare metal clusters, and the National Science Foundation for the study of chemisorbed cluster surfaces.

REFERENCES

1. S. C. O'Brien, Y. Liu, Q. Zhang, J. R. Heath, F. K. Tittle, R. F. Curl, and R. E. Smalley, J. Chem. Phys. 84 (1986) 4074.
2. Y. Liu, Q. L. Zhang, F. K. Tittle, R. F. Curl, and R. E. Smalley, J. Chem. Phys. 85 (1986) 7434.
3. M. M. Kappes, M. Schar, U. Rothlisberger, C. Yeretdzian, and E. Schumacher, Chem. Phys. Lett. 143 (1988) 251.
4. W. Saunders, K. Clemenger, W. de Heer and W. Knight, Phys. Rev. B 32 (1985) 1366.
5. O. Cheshnovsky, K. J. Taylor, J. Conceicao, and R.E. Smalley, Phys. Rev. Lett. 64 (1990) 1785.
6. K. J. Taylor, C. L. Pettiette, O. Cheshnovsky, and R. E. Smalley, J. Chem. Phys., submitted.
7. J. S. Blakemore in Gallium Arsenide, J. S. Blakemore, editor, American Institute of Physics (1987), pp 3-62.
8. X. Zhu, S. B. Zhang, S. G. Louie, and M. L. Cohen, Phys. Rev. Lett. 63 (1989) 2112.
9. J. van Laar, A. Huijser and T. L. van Rooy, J. Vac. Sci. Technol. 14 (1977) 894.
10. R. M. Feenstra, J. A. Stroscio, J. Tersoff, and A. P. Fein, Phys. Rev. Lett. 58 (1987) 1192.
11. W. R. Gentry in Atomic and Molecular Beam Methods, Vol. 1, edited by G. Scoles, Oxford U.P. (1988) pp 64-66.
12. M. G. Liverman, S. M. Beck, D. L. Monts, and R. E. Smalley, Rarefied Gas Dynamics 11 (1979) 192. A commercial version derived from this pulsed valve design is available from R. M. Jordon Company, Grass Valley, California.
13. C. W. S. Conover, Y. J. Twu, Y. A. Yang, and L. A. Bloomfield, Rev. Sci. Instrum. 60 (1989) 1065.
14. O. Cheshnovsky, S. H. Yang, C. L. Pettiette, M. J. Craycraft, and R. E. Smalley, Rev. Sci. Instrum. 58 (1987) 2131.
15. L. Wang, L. P. F. Chibante, F. K. Tittle, R. F. Curl, and R. E. Smalley, Chem. Phys. Lett., submitted.
16. H. Hotop and W. C. Lineberger, J. Chem. Phys. 58 (1979) 2379.
17. C. E. Moore, Atomic Energy Levels vol. III (Nat. Bur. Stand., 1971).
18. G. W. Lemire, G. A. Bishea, S. A. Heidecke, and M. D. Morse, J. Chem. Phys. 92 (1990) 121.

19. K. Balasubramanian, J. Chem. Phys. 86 (1987) 3410.
K. Balasubramanian, J. Mol. Spectroscopy 139 (1990) 405.
20. G. Scuseria, Private Communication.
21. Liang Lou, L.P.F. Chibante, L. Wang, and R. E. Smalley, unpublished results.
22. see for example, G. Makov, A. Nitzan, and L. E. Brus, J. Chem. Phys. 88 (1988) 5076.

FIGURE CAPTIONS

FIGURE 1. Photoelectron spectra of mass-selected Ga_xAs_y^- clusters near the composition $x=y$ as a function of cluster size, $n = x+y$, in the range $n=2-19$ atoms. The spectra were recorded using a F_2 excimer photodetachment laser (photon energy 7.9 eV).

FIGURE 2. Photoelectron spectra of mass-selected Ga_xAs_y^- clusters in the 20-37 atom size range.

FIGURE 3. Photoelectron spectra of mass-selected Ga_xAs_y^- clusters in the 38-50 atom size range.

FIGURE 4. Vertical electron affinity of Ga_xAs_y clusters near the $x=y$ composition as estimated from photoelectron spectra of the mass-selected negative cluster ions.

FIGURE 5. Photoelectron spectra of 23 atom Ga_xAs_y^- clusters at the masses approximately corresponding to (x,y) compositions of (18,5), (12,11) and (5,18), respectively.

TABLE I. Estimated vertical electron affinities of Ga_xAs_y^- clusters as a function of cluster size, $n = x+y$.

Cluster size	EA (eV)	Cluster size	EA (eV)	Cluster size	EA (eV)
2	2.1	19	3.4	36	3.7
3	1.9	20	3.1	37	4.3
4	2.1	21	3.5	38	3.6
5	2.3	22	3.2	39	4.3
6	2.1	23	3.8	40	3.7
7	3.1	24	3.4	41	4.3
8	2.3	25	4.0	42	3.9
9	3.3	26	3.4	43	4.3
10	2.7	27	3.9	44	3.9
11	3.2	28	3.4	45	4.3
12	2.8	29	4.0	46	3.8
13	3.3	30	3.6	47	4.2
14	2.9	31	4.1	48	4.0
15	3.3	32	3.6	49	4.2
16	2.9	33	4.1	50	3.9
17	3.5	34	3.6		
18	3.2	35	4.2		

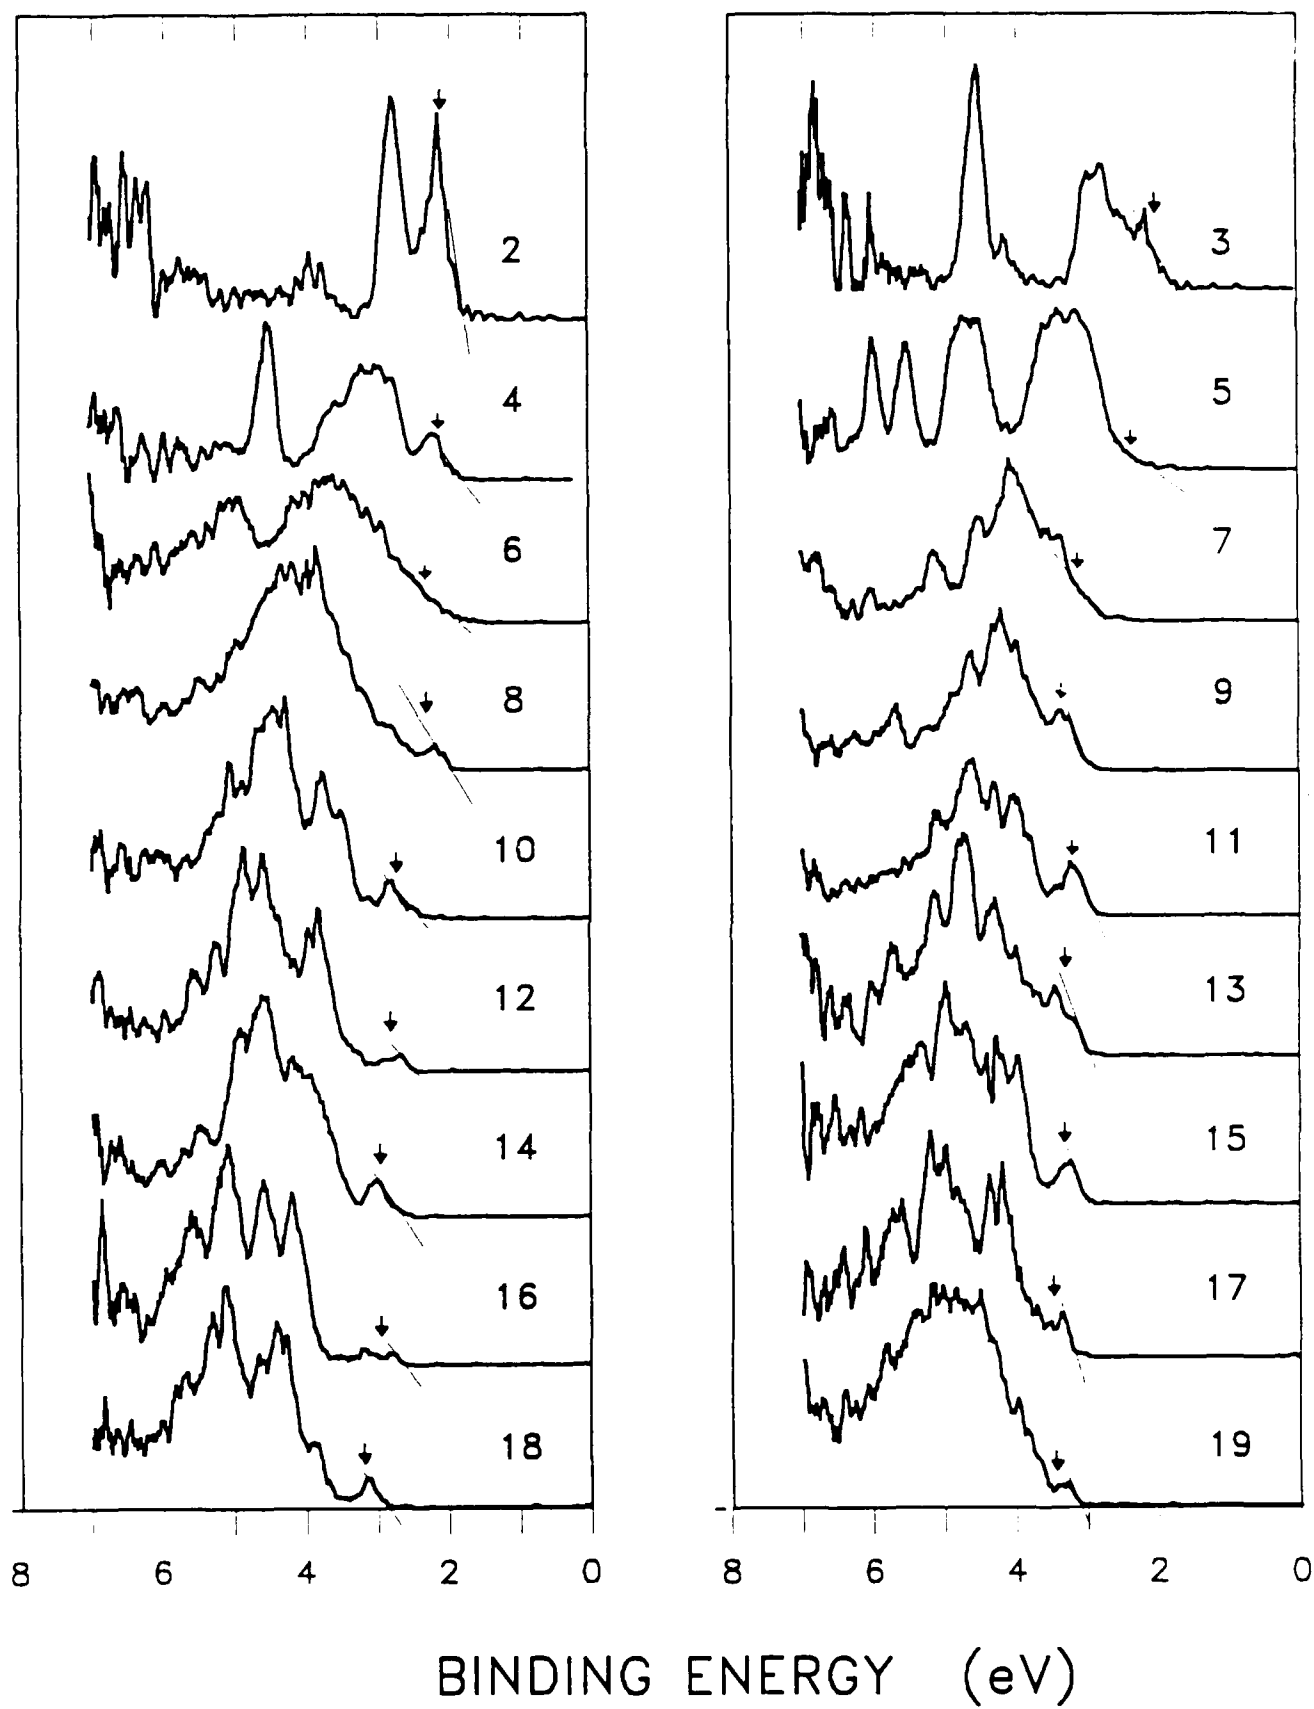


Fig.1

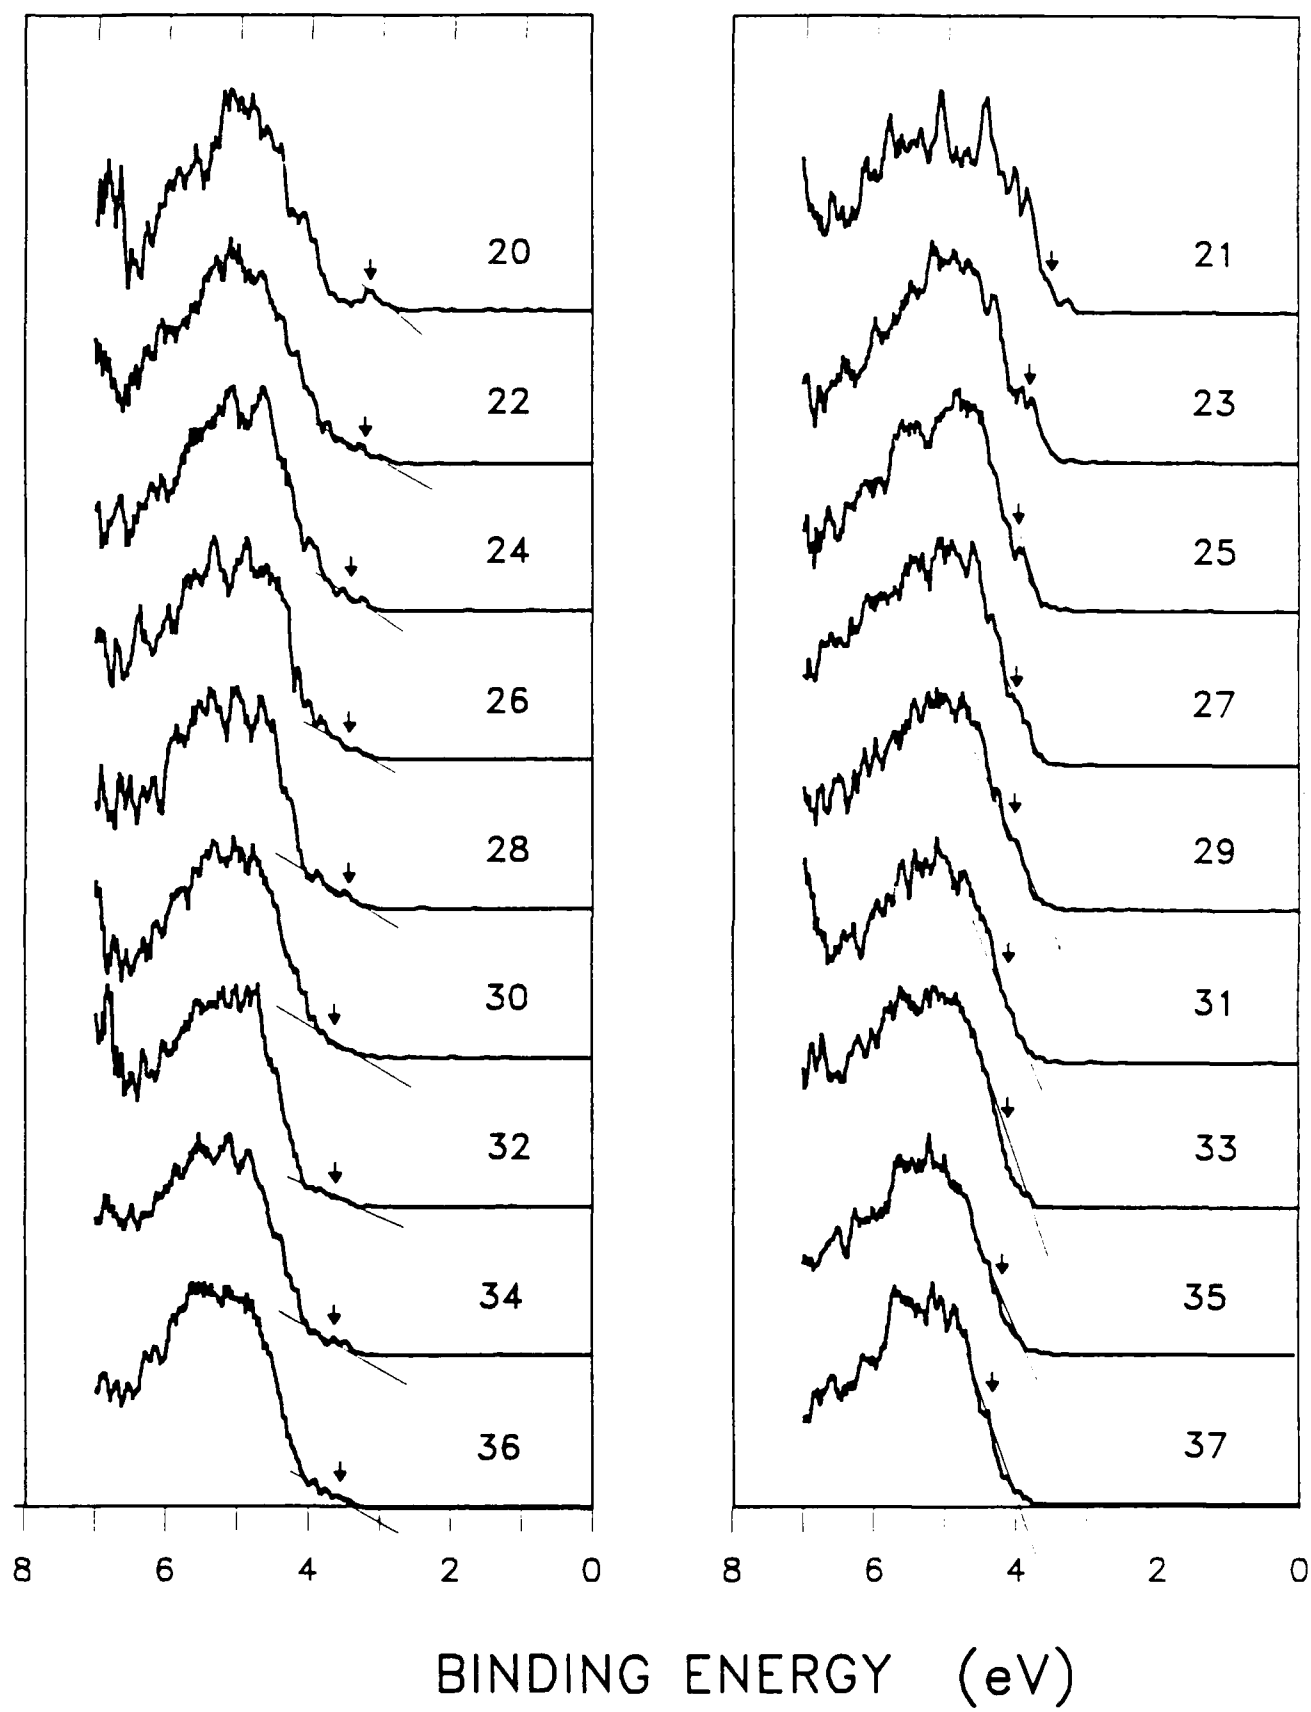


Fig. 2

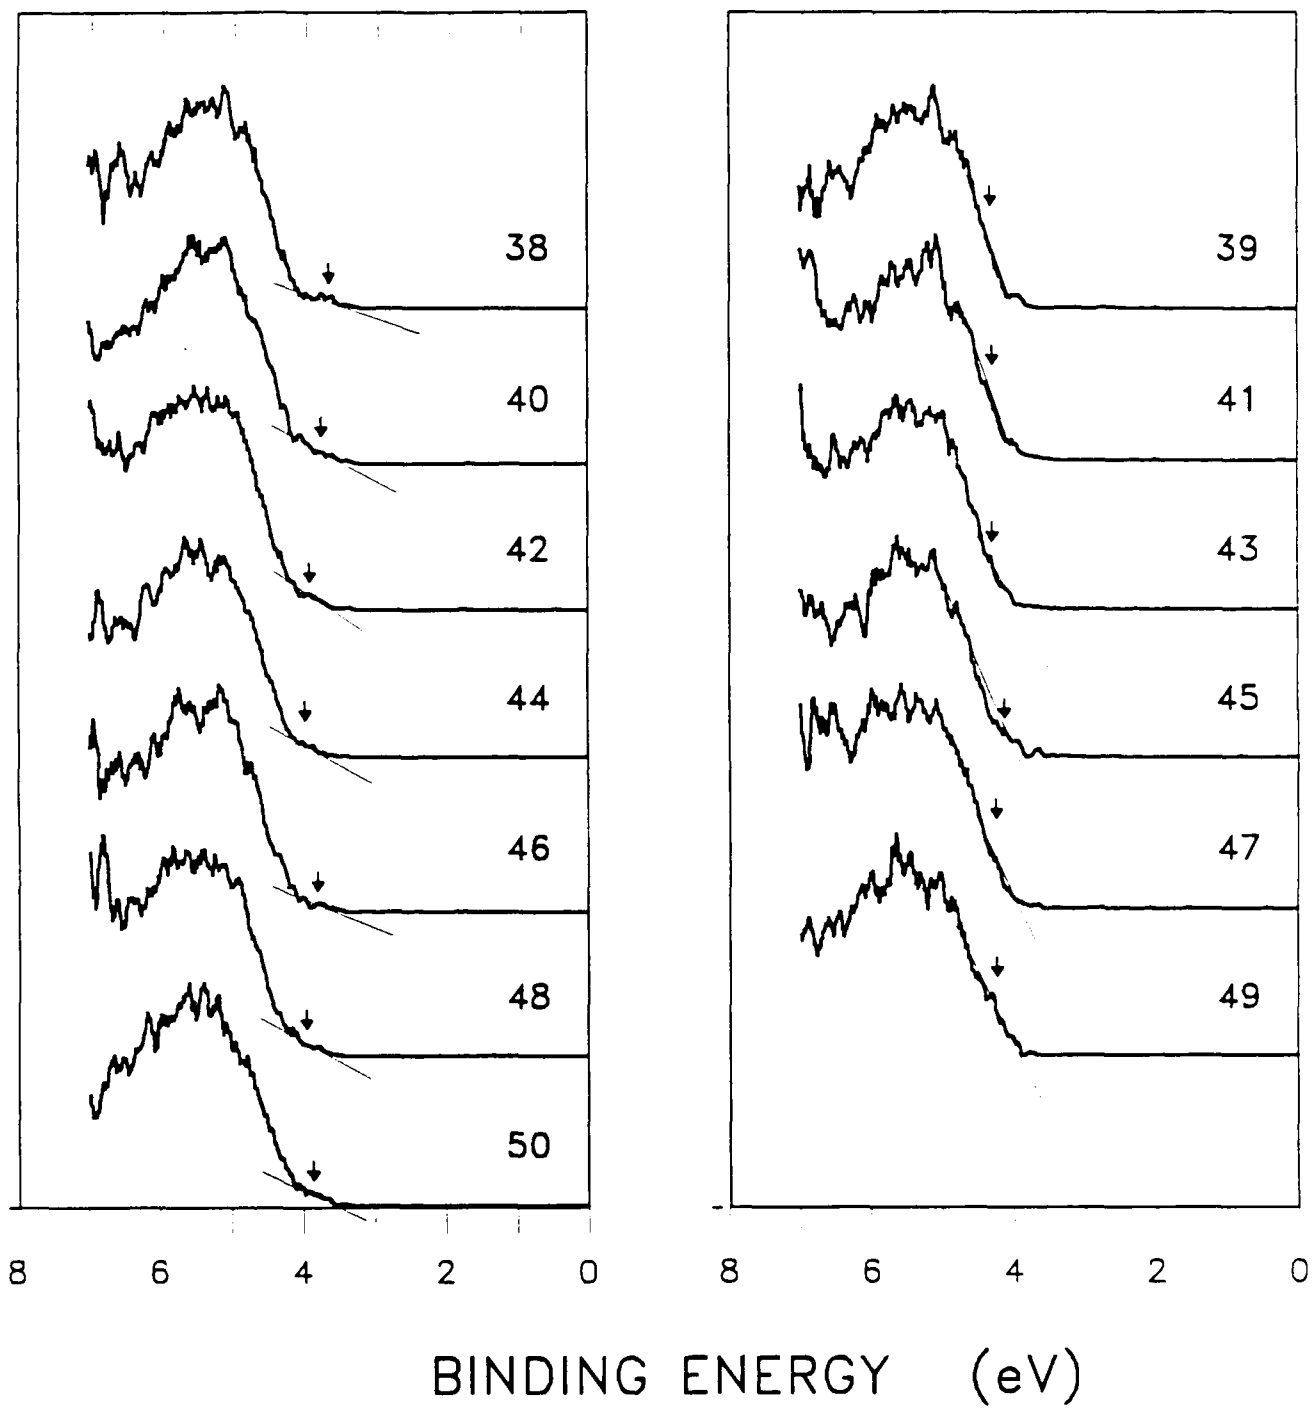


Fig. 3

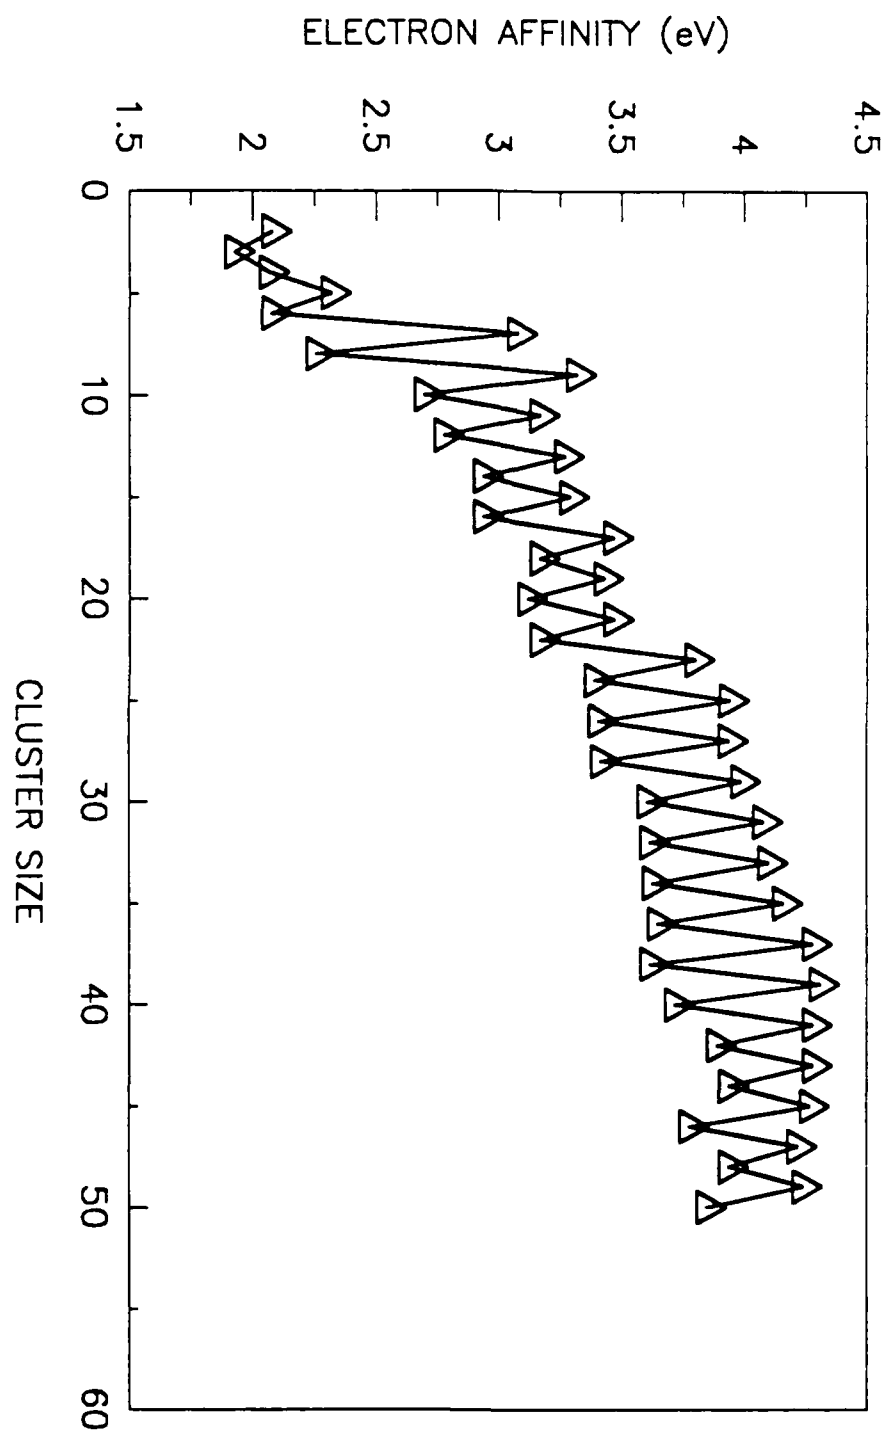


Fig. 4

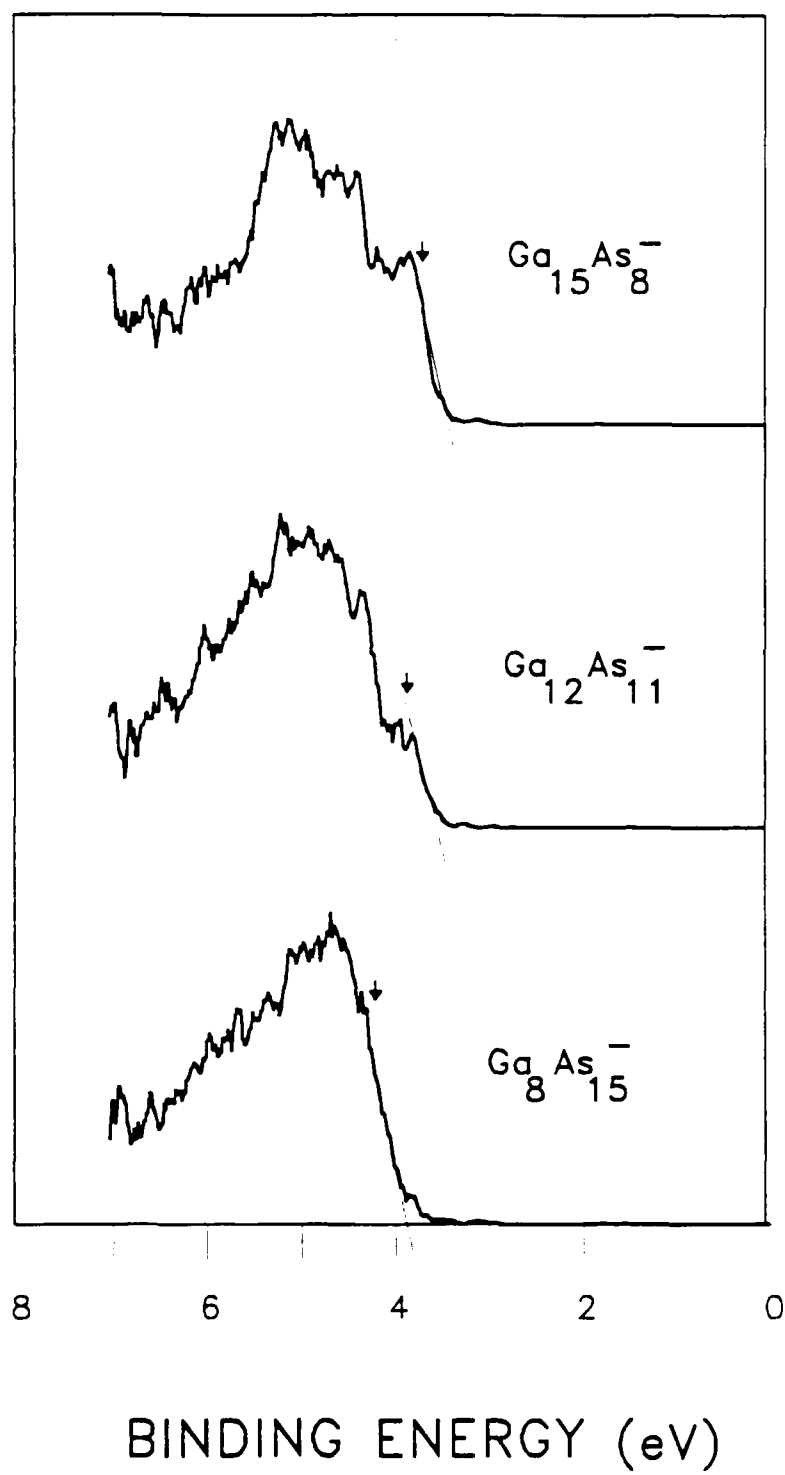


Fig. 5